

ESRF	Experiment title: Fermi surface and electron-electron correlation in CrV alloys	Experiment num_____: HE-276
Beamline: ID15B	Date of experiment: from:09-Sep-97 to:20-Sep-97	Date of report: 26.02.98
Shifts: 33	Local contact(s): Thomas Buslaps	<i>Received at ESRF:</i> 02 MAR. 1998

Names and affiliations of applicants (* indicates experimentalists):

Genevieve Loupiau *, Universite Paris 6, LMCP
 Christophe Bellin*, Universite Paris 6, LMCP
 Stephen Dugdale*, Universite de genève, DPMC
 Nobuhiro Shiotani*, Dpt of Physics, University of Fisheries, Tokyo

Report: (cf report on pure Cr, HE-62)

The Cr85V15 measurements have been the second step of our systematic study of the change of the geometry of the Fermi surface with V concentration. Moreover, the magnetic order of the chromium is linked to the Fermi surface topology.

The experiment has been performed with the scattering angle settled at 160° and the synchrotron radiation has been monochromatized at 55.9159 keV. We have measured 9 directional Compton profiles (DCPs) in order to reconstruct the momentum electronic density in the (110) plane. Such a reconstruction allows us to follow the details of the Fermi surface shape. In particular, the electronic hole depth at the N point moves with V concentration.

The data sets have been corrected for energy dependent effects such as photoelectric absorption in sample, analyser and air (photon path between sample, analyser and detector) by using a local correction algorithm (P.Fajardo, T.Buslaps, ESRF).

Due to the flatness of core profile in momentum space, it is easy to subtract its


contribution alone from the total measured DCP in order to get the valence DCP of interest.

Experimental valence profiles are normalized to the number of valence electrons of Cr85V15.

We follow the same way than for pure Cr (Let us notice that it is the first time, in the case of pure Cr, that the long tails of DCPs have been successfully used for reconstruction of the 2D map) :

a) at a first step, we make the difference between two directional profiles. Many of the systematic errors cancel when one profile is subtracted from another, in experiment as well as in theory. Such a difference profile gives us the anisotropy of the electronic density for two directions.

On figure 1, the experimental anisotropy, between [100] and [110] directions, is reported.

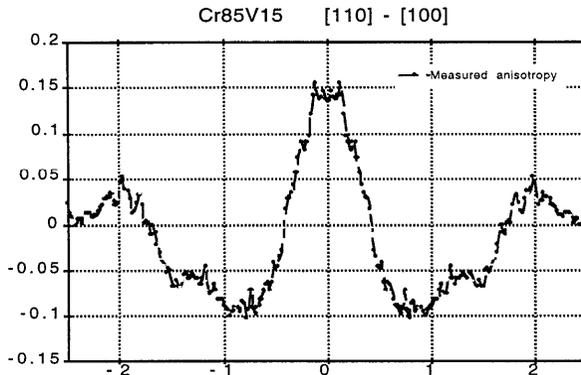

b) the second step is to reconstruct the 2D map of the electronic density in momentum space. Such a reconstruction has been successfully done, as noticed above, for pure Cr [Kai-Ji Chen thesis, Universite Paris 11, Orsay (1997)] and allowed us to find structures which were not seen in positron annihilation experiment. This reconstruction is under progress for Cr85V15.

The preliminary results look promising.

Moreover, calculations of directional Compton profiles using KKR method (Prof. Nakao, Tokyo) corresponding to the one measured at ESRF are under progress. Such calculations will allow us to make comparison between measurements and theory for both difference profiles (anisotropies) and 2D-maps in (110) plane.